



Original article

## Numerical Determination of the Life of Steel Exposed To Low Cycle Fatigue

\*Vujadin Aleksić<sup>a</sup>, Srđan. Bulatović<sup>a</sup>, Bojana Zečević<sup>b</sup>, Ana Maksimović<sup>b</sup>, Ljubica Milović<sup>c</sup>

<sup>a</sup> Institute for testing of materials-IMS Institute, Bulevar vojvode Mišića 43, 11000 Belgrade, Serbia

<sup>b</sup> Innovation Centre of the Faculty of Technology and Metallurgy, Karnegijeva 4, 11120 Belgrade, Serbia

<sup>c</sup> University of Belgrade, Faculty of Technology and Metallurgy, Karnegijeva 4, 11120 Belgrade, Serbia

### ABSTRACT

*In the paper, based on the results of the experimental research of high-strength low-alloy steel (HSLA), Nionical 70 (NN-70), under conditions of low-cycle fatigue (LCF), a numerical analysis of stress and determination of the life of steel samples was performed. Experimental testing of the behavior of the samples were performed with controlled and fully reversible strain ( $\Delta\varepsilon/2 = \text{const}$ ,  $R_\varepsilon = \varepsilon_{\min}/\varepsilon_{\max} = -1$ ), according to the standard ISO 12106:2003 (E). For computational analyses, the following were used: the method of least squares and the method of finite elements (FEM). On the basis of the analysis of the results of the stress-deformation state and the determination of the life span through the isolines of the life span and comparison with the results of experimental tests, a graphic representation is given. The analysis justified the effort to numerically solve the estimation of the lifespan of steel under low cycle fatigue (LCF).*

**Key words:** Steel, LCF, Lifetime, Numerical methods

### 1. INTRODUCTION

Low-cycle fatigue of material means low-frequency material fatigue in which the appearance of microcracks and fractures occurs during repeated plastic strain with the number of cycles to failure  $N = 5 \times 10^4$  changes. Low-cycle fatigue is often referred to as statistical endurance under repeated static loads. The characteristics of the fatigue process during low-cycle fatigue differ from the characteristics of the fatigue process during high-cycle fatigue for the same load levels, so the assessment of the suitability of the material for long-term work must include two types of tests: high-cycle fatigue with high frequency (high frequency value) and low-cycle fatigue at lower frequency values.

Experiences have shown that the time of crack initiation is

relatively short, so the life of the structure is usually determined according to the time of crack development, or more precisely, according to the time of development to the critical length of the crack.

### 2. TESTED MATERIAL

HSLA steel, NN-70 [1] is the Yugoslav version of the American steel HY-100. HSLA steels are generally being used for producing of ship and pressure equipment. The most significant component that influences steel selection is the suitable strength-to-weight proportion of HSLA steels compared with regular low-carbon steels. Ship structures are most commonly being produced by welding. For this reason high strength low-alloy (HSLA) steels, besides high strength as the main properties, should also

\* Corresponding author's e-mail: [vujadin.aleksic@institutims.rs](mailto:vujadin.aleksic@institutims.rs)

have exceptional plasticity, adequate toughness and high resistance to brittle damage, as well as adequate workability and good welding performance [2 - 5]. Due to exposure to complex loading with constant cycles during

exploitation, a basic understanding of material behavior and damage mechanisms under fatigue conditions is important. Tables 1 and 2 show the chemical composition and mechanical properties of HSLA steel NN-70.

Table 1. Chemical composition (%wt) of NN-70 [6 - 29]

C	Si	Mn	P	S	Cr	Ni	Mo	V	Al	As	Sn
0.106	0.209	0.220	0.005	0.0172	1.2575	2.361	0.305	0.052	0.007	0.017	0.014
Cu	Ti	Nb	Ca	B	Pb	W	Sb	Ta	Co	N	C <sub>eq</sub>
0.246	0.002	0.007	0.0003	0	0.0009	0.0109	0.007	0.0009	0.0189	0.0096	0.542

$$C_{eq} = C + Mn/6 + Si/24 + Ni/40 + Cr/5 + Mo/4 + V/14.$$


Table 2. Mechanical properties of NN-70 at room temperature, 20 °C, [6 - 29]

Microstructure	Tempered martensite + tempered bainite	
Ultimate tensile stress, R <sub>m</sub> , MPa	854.8	
Yield stress, R <sub>p0.2</sub> , MPa	813.4	
Modulus of elasticity, E, GPa	static	211.5
	dynamic, LCF	221.4
Percent elongation, A <sub>5</sub> , %	18.4	
Impact toughness, J/cm <sup>2</sup>	96.83	
Crack initiation energy, J/cm <sup>2</sup>	39.60	
Crack propagation energy, J/cm <sup>2</sup>	57.23	
Hardness	plate	245-269 HV30
	LCF specimen	252-262 HV10


### 3. MATERIAL TESTING

Tests of steel, NN-70, by low-cycle fatigue with half-amplitude of controlled deformation,  $\Delta\epsilon/2=0.35 - 0.80$ , were performed on 10 round smooth test samples (RSTS), Fig. 1a, made of sticks, 11x11x95 mm from steel plate NN-70, processed according to the drawing shown in Fig. 1b.

Low cycle fatigue test, in accordance with ISO 12106:2017 (E) [30], was performed on a universal servo-hydraulic MTS machine (rating 500 kN), in the Military Technical Institute in Žarkovo [10, 18]. The test results of 4 samples with controlled strain regimes shown in Table 3 were considered.

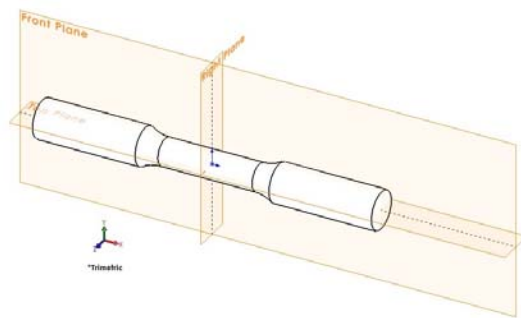

a) symmetry in three planes

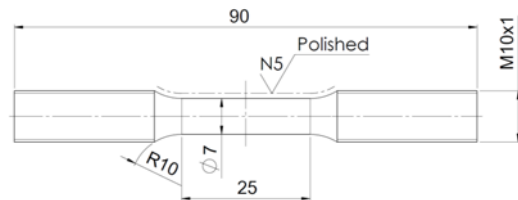

b) geometry of the specimen

Fig. 1 Specimen for LCF test of steel NN-70 [6, 29]

Table 3. Basic data on controlled strain regimes of LCF test NN-70 [18]

RSTS	1	2	3	4	5	6	7
	$\Delta\epsilon/2$ [%]	$\Delta\epsilon/2$ [V]	$\Delta\epsilon/2$ [mm/mm]	$\Delta l$ [mm]	$\Delta\epsilon$ [%]	T [s]	f [Hz]
	test	$\epsilon[\%] = \epsilon[V] \cdot 0.2$	1/100	3*25	1*2	test	1/6
09	0.35	1.75	0.0035	0.0875	0.70	4.30	0.2326
03	0.50	2.50	0.0050	0.1250	1.00	4.30	0.2326
06	0.60	3.00	0.0060	0.1500	1.20	4.30	0.2326
08	0.80	4.00	0.0080	0.2000	1.60	4.30	0.2326

The test results were processed using the EXCEL program [15, 16, 18, 26]. The results of that processing are shown in Tables 4 and 5, as well as Figures 2, 3, and 4.


**Table 4** Characteristic processed test data of LCF steel NN-70 [25, 26]

LCF NN-70, ISO 12106 [30]		Stabilization regions		Characteristic cycles of stabilization			
RSTS	$\Delta\epsilon/2, \%$	$y=F, \text{ kN}; x=N$	$R^2$	$N_{bs}$	$N_{es}$	$N_f$	$N_s = N_f/2$
09	0.35	$F=-0.0002N+24.30$	0.95	812	6740	8329	4165
03	0.50	$F=-0.0022N+28.57$	0.97	256	1271	1402	701
06	0.60	$F=-0.0057N+29.66$	0.94	127	415	501	251
08	0.80	$F=-0.0162N+30.83$	0.94	50	165	207	104

$N_{bs}$  –The beginning of stabilization;  $N_{es}$  – End of stabilization;  $N_f$  – Cycle of failure;  $N_s$  – Characteristic stabilization cycle

**Table 5.** Calculated LCF elastic and plastic strain amplitude components of NN-70 steel at characteristic  $N_s$  [25, 26]

RSTS	$y=mx-b; y=F, \text{ kN}; x=\Delta\epsilon_p/2$ $F=0; \Delta\epsilon_p/2=b/m$ $\Delta\epsilon_e/2=\Delta\epsilon/2-\Delta\epsilon_p/2$	$N_s$	$\Delta\epsilon/2$	$\Delta\epsilon_p/2$	$\Delta\epsilon_e/2$	$\sigma_{max}, \text{ MPa}$	$\sigma_{min}, \text{ MPa}$	$\Delta\sigma/2, \text{ MPa}$
09	$\Delta\epsilon_p/2=(3.04/61.38)/100$	4165	0.0035	0.000495	0.003005	608.14	-689.48	648.81
03	$\Delta\epsilon_p/2=(18.74/109.15)/100$	701	0.0050	0.001717	0.003283	702.84	-707.19	705.01
06	$\Delta\epsilon_p/2=(16.93/76.92)/100$	251	0.0060	0.002201	0.003799	736.15	-698.00	717.07
08	$\Delta\epsilon_p/2=(27.97/65.04)/100$	104	0.0080	0.004301	0.003699	761.87	-709.04	735.46

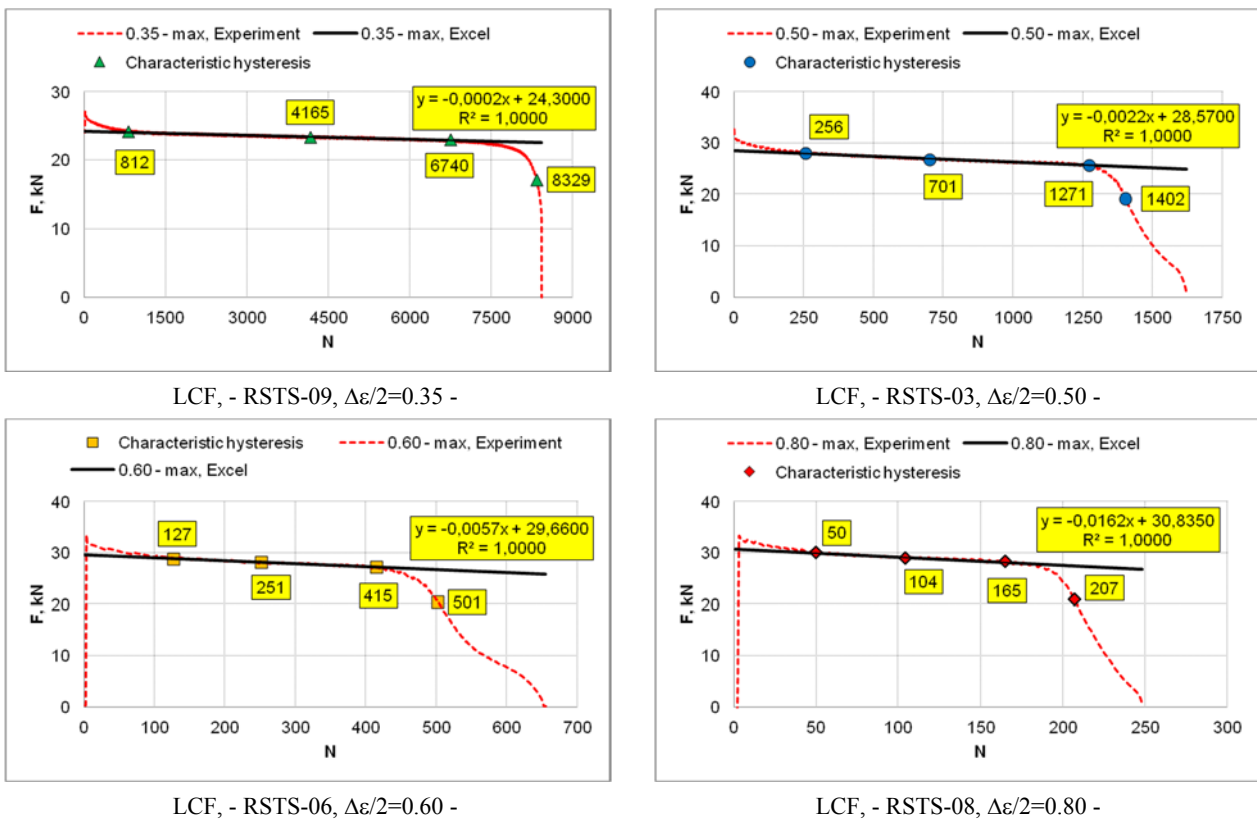

**Fig. 2** Graphical results of LCF test of NN-70 steel samples [25, 26]

#### 4. FEM SIMULATION

The data from Table 2 and the data derived from processing the results of the low cycle fatigue (LCF) test using Excel were employed for the static and fatigue calculations of the Finite Element Method (FEM) model of the parent material (PM) specimen within the Cosmos module of the SolidWorks parametric program. These inputs are illustrated in Fig. 5. An illustration of the results of the

calculation for a load of 27 kN (RSTS) is shown in Fig. 6 and Table 6. The SolidWorks program provides various analyses for the FEM static calculation, including the evaluation of Mises stress distribution and the assessment of normal stresses, strains, and elongations. Concerning fatigue calculation, it offers information on the minimum and maximum number of iso-sections within the lifecycle and the percentage of damage for a specific section of the test specimen. The methodology delineating the cycle

count for reaching the critical point of fracture under a particular load (RSTS) is depicted in Fig. 6, while the results obtained from this methodology are detailed in Table 6. The iso-section, encompassing the complete ligament of the test specimen and lying between the

minimum and maximum lifecycle cycles, signifies the cycle at which the fracture occurs.

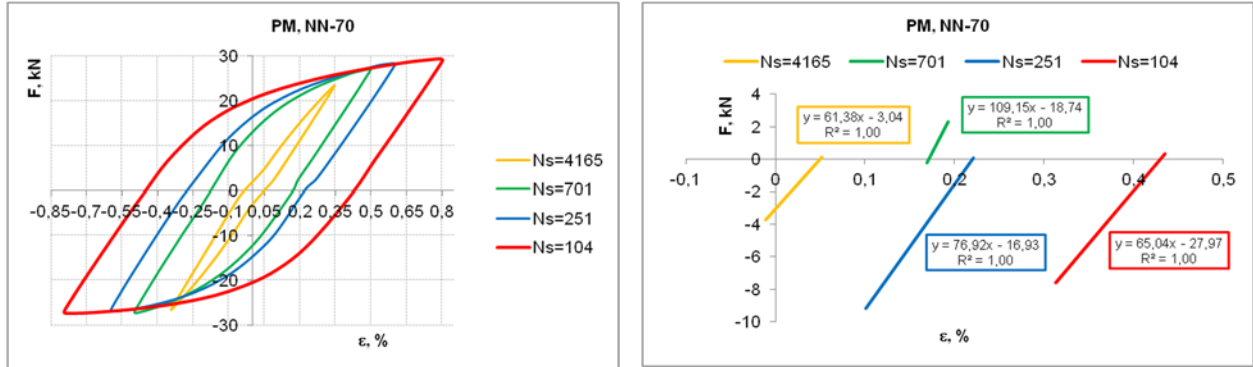


Fig. 3 Graphic view of processed stabilized hysteresis, Ns, LCF testing of HSLA steel NN-70 [25, 26]



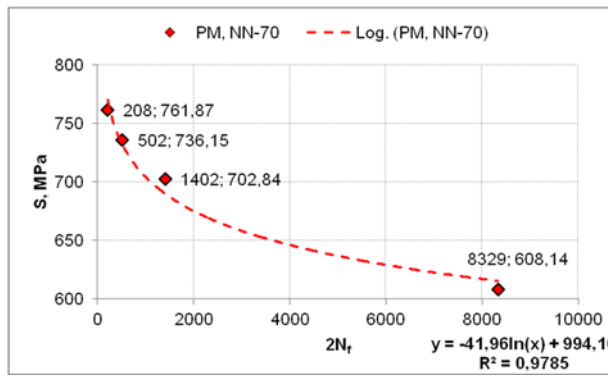


Fig. 4. Dependence  $S(\sigma)-2N_f$  obtained in EXCEL by the method of least squares [25, 26]

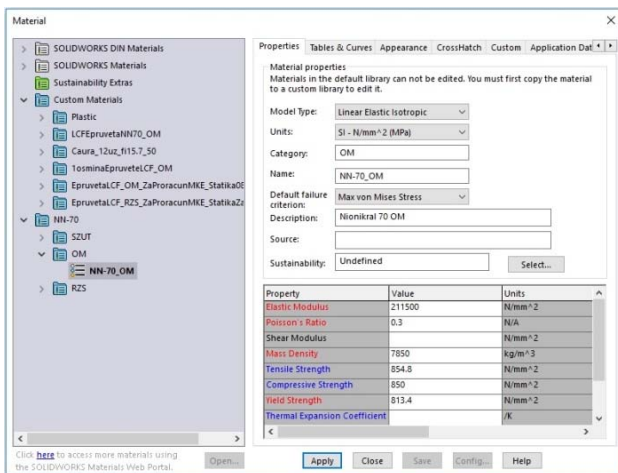

a) Input data for static calculation

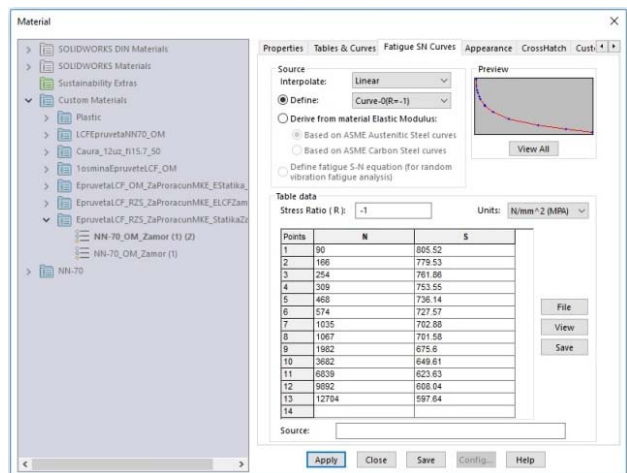


b) Input data for LCF calculation

Fig. 5 Data for FEM calculation static and dynamic behaviour of HSLA steel NN-70

**Table 6.** Results of static calculation and simulation of LCF fatigue FEM in SolidWorks, RSTS of HSLA steel NN-70

Testing specimen, cross section = 38.5 mm <sup>2</sup>						FEM		
LCF, Test		N <sub>fExcel</sub>	F, kN	S <sub>Nt</sub> , MPa	N <sub>fFEM</sub>	S <sub>NfFEM</sub> , max, MPa		
Δε/2	N <sub>fTest</sub>					Mizes	Normal	
NN-70		90	31.00	805.52	91	872.08	898.71	
		166	30.00	779.53	166	843.94	869.72	
	0.80	208	254	29.32	761.87	254	824.81	850.01
		309	29.00	753.55	309	815.81	840.73	
	0.60	502	468	28.33	736.15	468	796.96	821.31
		574	28.00	727.57	573	787.68	811.74	
	0.50	1402	1035	27.05	702.84	1034	760.96	784.20
		1067	27.00	701.58	1065	759.55	782.75	
		1982	26.00	675.60	1979	731.42	753.76	
		3682	25.00	649.61	3676	703.29	724.77	
		6839	24.00	623.63	6829	675.16	695.78	
	0.35	8329	9892	23.40	608.14	9876	658.28	678.38
		12704	23.00	597.64	12681	647.02	666.79	

$S_{Nf} = -41,96\ln(N_f) + 994,15$  (from formula in Fig. 4)

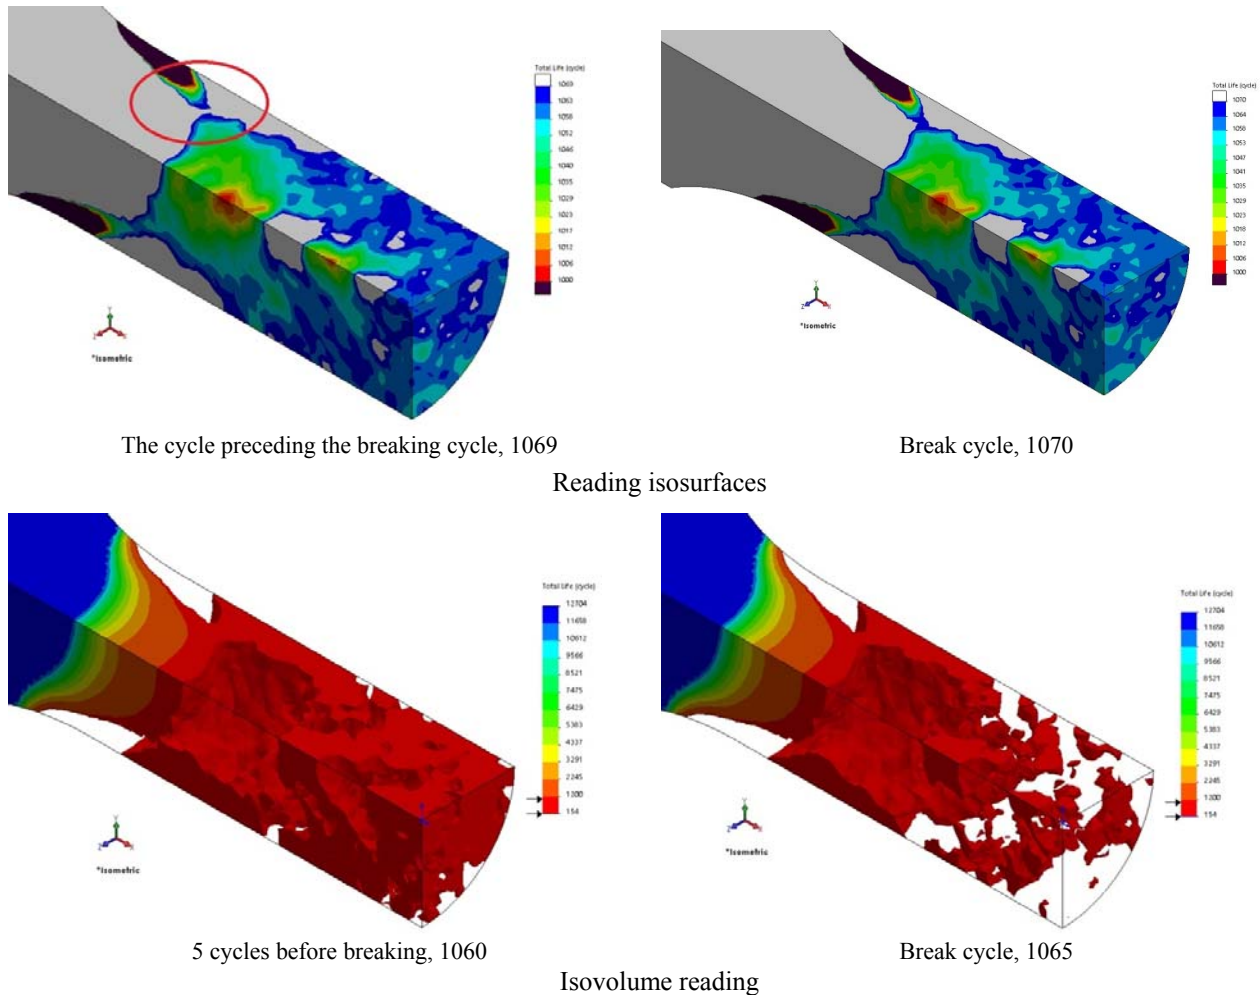

**Fig. 6** Determination of the failure cycle of RSTS HSLA steel NN-70 for a load of 27 kN (see table 6)

**5. DISCUSSION OF RESULTS**

By utilizing the least squares method in the EXCEL programs and employing the FEM in SolidWorks, we processed the outcomes of the LCF test and calculations.

This process provided the essential data required to determine: (a) cyclic stress-strain curve (1), Table 7 and Fig. 7, and (b) fatigue life curve (2) and transition fatigue life (3), N<sub>fT</sub>, Table 8 and Fig. 8.

Table 7. Data for Cyclic stress-strain curve (1) of HSLA steel NN-70

$\Delta\varepsilon = \frac{\Delta\sigma}{E} + 2\left(\frac{\Delta\sigma}{2K'}\right)^{\frac{1}{n'}} \quad (1)$	Method	n'	K', MPa	E, MPa, (from $N_{1/4}$ cycle)
	Standard [30]	0.047	946.2	221378 (221.4 GPa)

Table 8. Data for fatigue life curve (2) and transition fatigue life of HSLA steel NN-70(3)

$\frac{\Delta\varepsilon}{2} = \frac{\sigma'_f}{E} N_f^b + \varepsilon'_f N_f^c \quad (2)$	Method	elastic part			plastic part		$N_{fr}$
		E, MPa	$\sigma'_f$ , MPa	b	$\varepsilon'_f$	c	
$N_{fr} = \left(\frac{\varepsilon'_f \cdot E}{\sigma'_f}\right)^{\frac{1}{b-c}} \quad (3)$	Standard [30]	221378	1153.8	-0.060	0.1045	-0.594	274

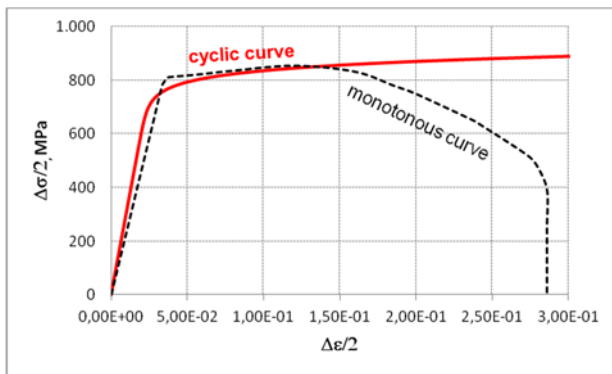


Fig. 7 Cyclic stress-strain curve of HSLA steel NN-70 (1)

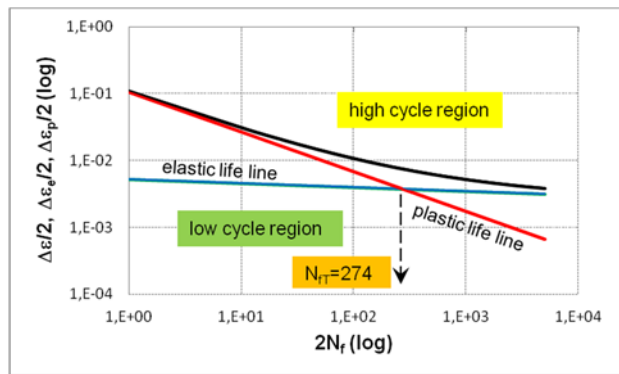


Fig. 8 Fatigue life curve (2) and transition fatigue life of HSLA steel NN-70 (3)

## 6. CONCLUSION

The paper outlines fatigue test results (LCF) conducted on a smooth, round test specimen using HSLA steel NN-70 as the base metal. These test results served as input data for low-cycle fatigue simulations on these samples, employing Finite Element Method (FEM) calculations in SolidWorks. The primary objective was to obtain comparative results for assessing the lifespan using both testing and FEM calculations. The methodology employed in determining the cycle count for specimen fracture in this study facilitates FEM-based calculations to predict fracture cycles for other components made from the same base metal subjected to low cycle fatigue loads (LCF).

One of the interesting and promising directions for future research involves applying the methodologies presented here to determine the size of fatigue cracks. This parameter stands as a crucial factor for characterizing fatigue existence, particularly under variable loading conditions. This approach aims to determine fatigue life, cycles until failure, and evaluate material resistance concerning crack initiation. Additionally, the progression of these cracks can also be tracked using Non-Destructive Testing (NDT) methods.

The stabilization phase observed during the LCF tests conducted on all samples of the HSLA steel NN-70 base metal exhibits a strong alignment with the general equation of a straight line,  $y (F \text{ or } \sigma) = m \times (N) + b$ . By employing linearization, the coefficients  $m$  and  $b$  can be derived, providing insight into the weakening trend within the HSLA steel NN-70 base metal.

These findings are valuable as they offer a practical contribution to assessing the behavior of high-strength, low-alloy NN-70 steel under LCF operating conditions.

## ACKNOWLEDGEMENTS

This work was supported by the Ministry of Education, Science and Technological Development of the Republic of Serbia (Contracts: No. 451-03-47/2023-02/200012 and No. 451-03-47/2023-01/200287).

## REFERENCES

- [1] Radović, A., Marković, D. (1984). Osvajanje Brodograđevnog Čelika Povišene Čvrstoće-Nionikral-70, VTI, Beograd.
- [2] Arpan, Das., Tamshuk, Chowdhury., Soumitra. Tarafder. (2014). Ductile fracture micro-mechanisms of high strength low alloy steels, *Materials and Design*, vol. 54, p. 1002–1009.
- [3] Tomasz, Ślęzaka., Lucjan, Śnieżeka., (2015). A Comparative LCF Study of S960QL High Strength Steel and S355J2 Mild Steel, *1st International Conference on Structural Integrity, Procedia Engineering*, vol. 114, p. 78– 85.
- [4] Abílio, M. P., De Jesus, A., Ribeiro, S., António, A. Fernandes. (2006). Low And High Cycle Fatigue and Cyclic Elastic-Plastic Behavior Of The P355n11 Steel, *Journal of Engineering Materials and*

- Technology, Transactions of the ASME*, vol. 128, p. 298-304.
- [5] Alang, N.A., Davies, C.M., Nikbin, K.M. (2016). Low cycle fatigue behaviour of ex-service P92 steel at elevated temperature, *21st European Conference on Fracture, ECF21*, Catania, Italy, *Procedia Structural Integrity*, vol. 2, p. 3177–3184.
- [6] Milović, Lj., Vuherer, T., Radaković, Z., Petrovski, B., Janković, M., Zrilić, M., Daničić, D. (2011). Determination of fatigue crack growth parameters in welded joint of hsla steel, *Structural integrity and life*, vol.11, no.3, p. 183-187.
- [7] Milović, Lj., Bulatović, S., Radaković, Z., Aleksić, V., Sedmak, S., Marković, S., Manjgo, M. (2012). Assessment of the behaviour of fatigue loaded HSLA welded steel joint by applying fracture mechanics parameters, *Structural integrity and life*, vol. 12, no. 3, p. 175–181.
- [8] Bulatović, S., Burzić, Z., Aleksić, V., Sedmak, A., Milović, Lj. (2014). Impact of choice of stabilized hysteresis loop on the end result of investigation of High-strength low-alloy (HSLA) steel on low cycle fatigue, *Metalurgija*, vol. 53, no. 4, p. 477–480.
- [9] Milović, Lj., Bulatović, S., Aleksić, V., Burzić, Z. (2014). Low cycle fatigue of weldments produced of a High strength low alloyed steel, *20th European Conference On Fracture (ECF 20)*, *Procedia Materials Science* 3, p. 1429–1434.
- [10] Bulatović, S. (2014). *Elasto-plastično ponašanje zavarenog spoja od niskolegiranih čelika povišene čvrstoće u uslovima niskocikličnog zamora*, (In Serbian). PhD thesis. Mašinski Fakultet Univerziteta u Beogradu.
- [11] Aleksić, V., Aleksić, B., Milović, Lj. (2016). Methodology for determining the region of stabilization of low-cycle fatigue, *Book Of Abstracts, 16th International Conference On New Trends In Fatigue And Fracture (NT2F16)*, Dubrovnik, Croatia, p. 189–190.
- [12] Aleksić, V., Milović, Lj., Aleksić, B., Abubkr, M. Hemer. (2016). Indicators of HSLA steel behavior under low cycle fatigue loading, *21st European Conference on Fracture, ECF21*, Catania, Italy, *Procedia Structural Integrity*, vol. 2, p. 3313–3321.
- [13] [Aleksić, V., Dojčinović, M., Milović, Lj., Samardžić, I. (2016). Cavitation damages morphology of HSLA Steel, *Metalurgija*, vol. 55, no. 3, p. 423–425.
- [14] Aleksić, V., Milović, Lj., Aleksić, B., Bulatović, S., Burzić, Z., Hemer, A.M. (2017) Behaviour Of Nionikral-70 In Low-Cycle Fatigue, *Structural integrity and life*, vol. 17, no. 1, p. 61–73.
- [15] Aleksić, V., Aleksić, B., Milović, Lj. (2017). Metodologija određivanja pokazatelja ponašanja hsla čelika pri delovanju niskocikličnog zamora, *V Međunarodni Kongres „Inženjerstvo, Ekologija I Materijali U Procesoj Industriji”*, Jahorina, Bosna I Hercegovina, p. 1123-1135.
- [16] Aleksić, B., Aleksić, V., Hemer, A., Milović, Lj., Grbović, A. (2018). Determination Of The Region Of Stabilization Of Low-Cycle Fatigue HSLA Steel From Test Data. In: *Proceedings Of The 17th International Conference On New Trends In Fatigue And Fracture*, Eds: Ricardo R. Ambriz, David Jaramillo, Gabriel Plascencia And Moussa Nait Abdelaziz, Springer, p. 101–113.
- [17] Aleksić, B., Aleksić, V., Milović, Lj., Hemer, A., Prodanović, A. (2018). Determination of polynomial depending between hardness and cooling time  $\Delta t_{8/5}$  of steel Nionikral 70 heat affected zone, *18th International Conference on New Trends in Fatigue and Fracture NT2F18*, Lisbon, Portugal, p. 87–90.
- [18] Aleksić, V. (2019). *Niskociklični Zamor Niskolegiranih Čelika Povišene Čvrstoće*, (In Serbian). PhD thesis. Tehnološko – Metalurški Fakultet Univerziteta U Beogradu.
- [19] Aleksić, V., Milović, Lj., Blačić, I., Vuherer, T., Bulatović, S. (2019). Effect of LCF on behavior and microstructure of microalloyed HSLA steel and its simulated CGHAZ, *Engineering Failure Analysis*, vol. 104, p. 1094–1106.
- [20] Aleksić, V., Aleksić, B., Prodanović, A., Milović, Lj. (2020). HSLA Steel-Simulation of fatigue, *New Technologies, Development And Application, Lecture Notes in Networks And Systems, Sarajevo*, vol 128. Springer, p. 314 – 321.
- [21] Bulatović, S., Aleksić, V., Milović, Lj., Zečević, B. (2021). An analysis of impact testing of high strength low-alloy steels used in ship construction, *Brodogradnja/Shipbuilding/Open Access*, vol. 72, no. 3, p. 1–12.
- [22] Bulatović, S., Aleksić, V., Milović, Lj., Zečević, B. (2021). High strength low alloy steels impact toughness assessment at different test temperatures, *Advanced Technologies & Materials*, vol. 46, no. 2, p. 43–46.
- [23] Bulatović, S., Aleksić, V., Milović, Lj., Zečević B. (2021). Determination of the coffin-manson equation under low-cycle fatigue conditions, *Structural integrity and life*, vol. 21, no. 3, p. 225–228.
- [24] Aleksić, V., Dojčinović, M., Milović, Lj., Zečević, B., Maksimović, A. (2021). Mehanizmi i morfologije kavitacionog oštećenja čelika Nionikral 70, *Zaštita Materijala*, vol. 62, no. 2, p. 95–105.
- [25] Aleksić, V., Milović, L., Bulatović, S., Zečević, B., Maksimović, A. (2022). Determination of LCF plastic and elastic strain components of steel, *Machine And Industrial Design In Mechanical Engineering. KOD 2021. Mechanisms And Machine Science, Balaton*, vol. 109. Springer, Cham. p. 341–349.
- [26] Aleksić, V., Bulatović, S., Zečević, B., Maksimović, A., Milović, Lj. (2022). Processing of data obtained by the testing of steel under Low cyclic fatigue (part I), *Transactions Of Famena*, vol. XLVI, no. 4, p. 59-72.
- [27] Bulatović, S., Aleksić, V., Milović, Lj., Zečević, B. (2022). Determining of the fatigue crack growth rate of HSLA steel at room temperature, *Advanced Technologies & Materials*, vol. 47, no. 1, p. 1–4.

- [28] Bulatović, S., Aleksić, V., Milović, Lj., Zečević, B. (2022). Application Of Paris' Law Under Variable Loading, *FME Transactions*, vol. 50, no. 1, p. 72–78.
- [29] Bulatović, S., Aleksić, V., Milović, Lj., Zečević, B. (2023). Experimental determination of the critical value of the J-integral that refers to the HSLA steel welded joint, *Tehnički Vjesnik/Technical Gazette*, vol. 30, no. 1, p. 148–152.
- [30] ISO 12106. (2017). *Metallic Materials-Fatigue Testing-Axial-Strain-Controlled Method*, Geneva, Switzerland.

**NOTE**

This paper is based on the paper presented at 16th International Conference on Accomplishments in Mechanical and Industrial Engineering - DEMI 2023, organized by University of Banja Luka, Faculty of Mechanical Engineering in Banja Luka, Bosnia & Herzegovina, 1st to 2nd June 2023, Banja Luka.